



Designation: D4585/D4585M – 18

Standard Practice for Testing Water Resistance of Coatings Using Controlled Condensation¹

This standard is issued under the fixed designation D4585/D4585M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 This practice covers basic principles and operating procedures for testing water resistance of coatings using controlled condensation. Condensation is produced by exposing one surface of a coated specimen to a heated, saturated mixture of air and water vapor, while the reverse side of the specimen is exposed to the cooling effect of room temperature air. This practice is derived from research of the Cleveland Society for Coatings Technology.²

1.2 This practice is limited to the methods of obtaining, measuring, and controlling conditions and procedures of controlled condensation tests. It does not specify specimen preparation, specific test conditions, or evaluation of results.

NOTE 1—Alternative practices for testing water resistance of coatings include Practices D870, D1735, and D2247.

1.3 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

¹ This practice is under the jurisdiction of ASTM Committee D01 on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee D01.27 on Accelerated Testing.

Current edition approved July 1, 2018. Published July 2018. Originally approved in 1986. Last previous edition approved in 2013 as D4585 – 13. DOI: 10.1520/D4585_D4585M-18.

² Foecking, N. J., "Cleveland Condensing Type Humidity Cabinet," *Official Digest*, December 1963, Vol 35, No. 467, pp. 1318–1327; and Higgins, W. A., "Cleveland Condensing Type Humidity Cabinet: II," *Official Digest*, November 1965, Vol 37, No. 490, pp. 1392–1404.

2. Referenced Documents

2.1 ASTM Standards:³

- D609 Practice for Preparation of Cold-Rolled Steel Panels for Testing Paint, Varnish, Conversion Coatings, and Related Coating Products
- D610 Practice for Evaluating Degree of Rusting on Painted Steel Surfaces
- D714 Test Method for Evaluating Degree of Blistering of Paints
- D823 Practices for Producing Films of Uniform Thickness of Paint, Coatings and Related Products on Test Panels
- D870 Practice for Testing Water Resistance of Coatings Using Water Immersion
- D1654 Test Method for Evaluation of Painted or Coated Specimens Subjected to Corrosive Environments
- D1730 Practices for Preparation of Aluminum and Aluminum-Alloy Surfaces for Painting
- D1735 Practice for Testing Water Resistance of Coatings Using Water Fog Apparatus
- D2247 Practice for Testing Water Resistance of Coatings in 100 % Relative Humidity
- D2616 Test Method for Evaluation of Visual Color Difference With a Gray Scale
- D3359 Test Methods for Rating Adhesion by Tape Test
- D3363 Test Method for Film Hardness by Pencil Test
- D4541 Test Method for Pull-Off Strength of Coatings Using Portable Adhesion Testers
- G154 Practice for Operating Fluorescent Ultraviolet (UV) Lamp Apparatus for Exposure of Nonmetallic Materials

3. Summary of Practice

3.1 Water vapor is generated by heating a pan of water at the bottom of the test chamber. The specimens form the roof or walls of the test chamber so that the back sides of the specimens are exposed to the cooling effects of room temperature air. The resulting heat transfer causes vapor to condense on the test specimens as liquid water saturated with air.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard



3.2 The temperature and amount of condensate forming on the specimens is controlled by the temperature differential between the test chamber and the room. The test specimens are inclined so that condensate runs off the test surface by gravity and is replaced by fresh condensate in a continuous process during the condensate cycle.

3.3 Exposure conditions are varied by selecting: (a) the temperature of the test, (b) the duration of the test, and (c) periodic drying of the specimens. Testing may be conducted at temperatures from 38 to 82°C [100 to 180°F]. Any effects such as color change, blistering, loss of adhesion, softening, or embrittlement are observed and reported.

4. Significance and Use

4.1 Water can cause degradation of coatings, so knowledge of how a coating resists water is helpful in predicting its service life. Failure in a condensation test may be caused by a number of factors including a deficiency in the coating itself, contamination of the substrate, or inadequate surface preparation. The test is therefore useful for evaluating coatings alone or complete coating systems.

4.2 Condensation tests of coatings are used for specification acceptance, quality control, and research and development of coatings and substrate treatments. These tests usually result in a pass or fail determination but the degree of failure also may be measured. A coating system is considered to pass if there is no evidence of water-related failure after a specified period of time.

4.3 Results obtained from the use of condensation tests in accordance with this practice should not be represented as being equivalent to a period of exposure to water in the natural environment, until the degree of quantitative correlation has been established for the coating or coating system.

4.4 The test is usually conducted on metal, plastics, or wood specimens with the coating facing the inside of the chamber. However, it is possible to test the blister resistance of house coatings on wood specimens by mounting the uncoated wood surface facing the inside of the chamber.

4.5 This practice can be used for corrosion tests particularly if the specimens are periodically dried. While corrosion products will drain into the water bath, they are not carried into the vapor that condenses on the test specimens.

5. Apparatus

5.1 *Test Chamber* (see Fig. 1 and Fig. 2), consisting of

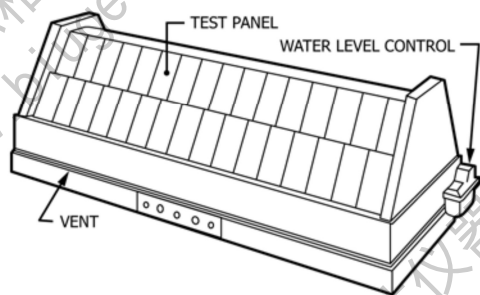


FIG. 1 Controlled Condensation Apparatus

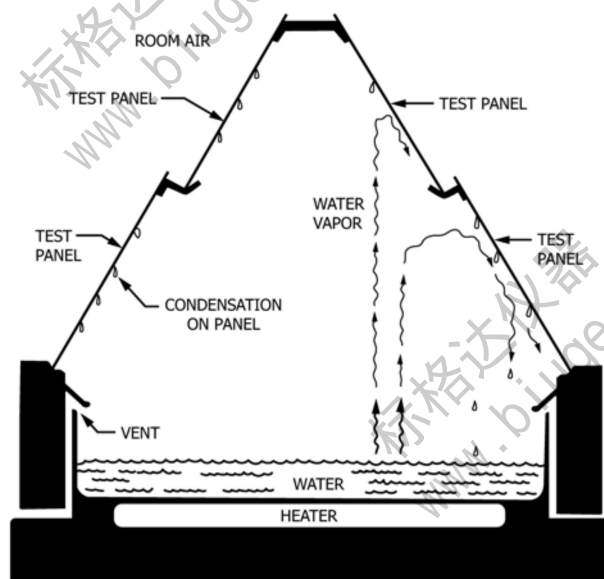


FIG. 2 Apparatus Cross Section

insulated side walls mounted on a base, test specimen racks attached to the side walls, a heated water pan, and provisions for controlling and indicating the vapor temperature within the chamber. Vents, approximately 3 to 5 mm [0.10 to 0.20 in.] wide, shall be provided to admit room air at the bottom of the test chamber. Locate the chamber away from air vents and direct drafts.

NOTE 2—The apparatus described in Practice G154 may be used if the ultraviolet lamps specified in Practice G154 are turned off.

5.2 Specimens shall form the roof of the test chamber. If the specimens cannot completely fill all the openings, blank panels shall be used. Certain substrates may deform from the heat and moisture. The specimens shall be mounted to eliminate gaps between specimens that allow heat and moisture to escape. Various types of tape can be used to seal the gaps that develop when the specimen deforms. Specimens shall be inclined from 15 to 75° from the horizontal and arranged so that condensate is returned to the water pan without dripping on other specimens.

5.3 *Water Supply*, with water level control.

5.4 *Water Heater*, preferably located under the water pan, controlled by a thermostat with the sensing element located in the water.

5.5 *Thermometer*, with the stem extending into the air-water vapor mixture in the test chamber.

5.6 *Program Timer, Blower, and Air Heater*, (optional) fitted to the chamber to provide periods of drying on a fixed schedule.

6. Test Specimens

6.1 This practice does not cover the preparation of test specimens. The substrate composition and surface preparation, specimen preparation, and the number of specimens should be agreed upon prior to testing.

NOTE 3—Applicable methods for the preparation of test panels and



substrates are given in Practice D609 and Practices D1730. Practices D823 cover application techniques for the production of uniform films.

6.2 It is recommended that a control specimen of a coating with known durability be included with each test. Such control specimens can provide warning of changes in test severity in a given apparatus, and can indicate variations in test severity between different apparatuses.

6.3 It is recommended that at least two replicate specimens of each different coating be used, so as to compensate for variations between specimens and variations in test conditions within the apparatus.

6.4 Test specimens should be flat rigid material. Minimum size is 76-mm [3-in.] wide and 152-mm [6-in.] tall. Maximum thickness is 19 mm [$\frac{3}{4}$ in.]. Materials thicker than 19 mm [$\frac{3}{4}$ in.] insulate and the condensate does not form on the tested side of the panel. If the test panels overshadow the upper shelf, do not put test panels on the upper shelf. Check the samples periodically to make sure condensation is occurring.

NOTE 4—A 3 mm glass plate in place of a sample will work to monitor whether condensation is occurring.

7. Procedure

7.1 Fill the water pan to a depth of approximately 25 mm [1 in.] with water. The quality of the water in the pan does not affect the test since the evaporation and condensation process yields distilled water, but the use of tap water can result in the accumulation of residues in the water pan.

7.2 Fill all spaces in the specimen holder rack with specimens or corrosion-resistant blank panels. Mount coated metal panels with the coating to be tested facing the inside of the chamber. Coated wood specimens may be mounted in the same way.

7.2.1 Blister tests to simulate the effects of water vapor migration from inside a frame house are mounted with the *uncoated* side of the wood specimen facing the inside of the test chamber.

7.2.2 Close all gaps between specimens and all holes in specimens, to prevent water vapor loss and local temperature variation. Condensate usually seals gaps or holes smaller than 1 mm [0.04 in.], but larger openings must be closed with tape, metal strips, or other suitable gap-filling materials.

7.3 Adjust the thermostat to maintain the desired temperature of the saturated air and water vapor mixture. Vapor temperatures of 38, 49, or 60°C [100, 120, or 140°F] are suggested. Other temperatures may be used provided that the temperature is reported in conformance with Section 8. To ensure adequate condensation, maintain at least a 11°C [20°F] temperature differential between the room and the vapor.

7.4 Operate the chamber continuously unless otherwise specified or agreed. The removal of specimens for inspections

during operation is permitted. When removing a specimen for inspection, replace it with a blank so that the test conditions are not altered.

7.5 Cyclic operation with alternating periods of condensation and drying may be used. Automatic drying requires the apparatus described in 5.6. For manual drying of specimens, remove them from the apparatus. Drying periods of at least 4 h long are recommended.

7.6 To control for variability within the apparatus, reposition the specimens on a regular basis so that all specimens spend equivalent amounts of time in the various areas of the apparatus (top, bottom, left, right, and center).

7.7 Conclude the test after a specified period of time or after effects from exposure to water are noted.

7.8 Remove specimens at the conclusion of the test. Do not leave the specimens in the apparatus at the conclusion of the test as the specimens can remain wet for hours, or even days, when the apparatus is turned off.

7.9 Wipe the test specimens dry. Rate specimens for changes in color, blistering, etc. Evaluate specimens no less than 5 min and no more than 10 min after removal from test, as the effects from water exposure can change within a short time. Remove only as many specimens as can be rated within the specified time.

NOTE 5— Relevant procedures for evaluating water effects are described in Test Methods D610, D714, D1654, D2616, D3359, D3363, and D4541.

7.9.1 If possible, rate the specimens again after they have been removed from the test for a recovery period long enough that moisture absorbed within the specimen dries out and the specimens reach moisture equilibrium with room air. A recovery period from 12 to 24 h is generally sufficient. The post-recovery rating allows evaluation of the permanent effects of the exposure as distinct from the transient effects, and is especially important for evaluation of color and gloss.

8. Report

8.1 Report the following information:

8.1.1 Sample identification.

8.1.2 Results of the evaluation(s).

8.1.3 Reference to Practice D4585.

8.1.4 Hours of test duration.

8.1.5 Description of any cyclic operations.

8.1.6 Condensation temperature.

8.1.7 Special conditions of test or any deviations in test procedure.

9. Keywords

9.1 adhesion; blistering; condensation; humidity; resistance-water; rust



SUMMARY OF CHANGES

Committee D01 has identified the location of selected changes to this standard since the last issue (D4585/D4585M-13) that may impact the use of this standard. (Approved July 1, 2018.)

- (1) Revised 3.2 to clarify that the temperature differential between the chamber and the room is what causes condensation.
- (2) Revised 6.2 and 6.3 from “it’s” to “it is.”
- (3) Revised 4.4 and 6.2 to harmonize in use of the word coatings, instead of paint.
- (4) Revised 6.4 to correct an error in conversion from English to SI units. $\frac{3}{4}$ in. maximum specimen thickness was originally specified in the standard, but was incorrectly converted to 8 mm (presumably, it should have been 18 mm). That is now being corrected to more accurately be 19 mm.
- (5) Revised 7.2.2 to change “crack” to “gap” and allow for use of other suitable gap-filling materials, which are commonplace in this type of testing.
- (6) Revised 7.5 to reword to eliminate use of “should” and clarify that drying periods of at least 4 hours are recommended.
- (7) Revised Note 5 to make sentence structure clearer.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>