



Standard Practice for Fluorescent UV-Condensation Exposures of Paint and Related Coatings¹

This standard is issued under the fixed designation D4587; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This practice covers the selection of test conditions for accelerated exposure testing of coatings and related products in fluorescent UV and condensation devices conducted according to Practices G151 and G154. This practice also covers the preparation of test specimens, and the evaluation of test results. Table 1 describes commonly used test conditions.

NOTE 1—Previous versions of this practice referenced fluorescent UV devices described by Practice G53, which described very specific equipment designs. Practice G53 has been withdrawn and replaced by Practice G151, which describes performance criteria for all exposure devices that use laboratory light sources, and by Practice G154, which gives requirements for exposing nonmetallic materials in fluorescent UV devices.

NOTE 2—ISO 11507:1997 also describes fluorescent UV-condensation exposures of paints and coatings.

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety problems associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:²

- D358 Specification for Wood to Be Used as Panels in Weathering Tests of Coatings (Withdrawn 2014)³
- D523 Test Method for Specular Gloss
- D609 Practice for Preparation of Cold-Rolled Steel Panels for Testing Paint, Varnish, Conversion Coatings, and

Related Coating Products

- D610 Practice for Evaluating Degree of Rusting on Painted Steel Surfaces
- D659 Method for Evaluating Degree of Chalking of Exterior Paints (Withdrawn 1990)³
- D660 Test Method for Evaluating Degree of Checking of Exterior Paints
- D662 Test Method for Evaluating Degree of Erosion of Exterior Paints
- D714 Test Method for Evaluating Degree of Blistering of Paints
- D772 Test Method for Evaluating Degree of Flaking (Scaling) of Exterior Paints
- D823 Practices for Producing Films of Uniform Thickness of Paint, Varnish, and Related Products on Test Panels
- D1005 Test Method for Measurement of Dry-Film Thickness of Organic Coatings Using Micrometers
- D1186 Test Methods for Nondestructive Measurement of Dry Film Thickness of Nonmagnetic Coatings Applied to a Ferrous Base (Withdrawn 2006)³
- D1400 Test Method for Nondestructive Measurement of Dry Film Thickness of Nonconductive Coatings Applied to a Nonferrous Metal Base (Withdrawn 2006)³
- D1729 Practice for Visual Appraisal of Colors and Color Differences of Diffusely-Illuminated Opaque Materials
- D1730 Practices for Preparation of Aluminum and Aluminum-Alloy Surfaces for Painting
- D2244 Practice for Calculation of Color Tolerances and Color Differences from Instrumentally Measured Color Coordinates
- D2616 Test Method for Evaluation of Visual Color Difference With a Gray Scale
- D3359 Test Methods for Measuring Adhesion by Tape Test
- D3980 Practice for Interlaboratory Testing of Paint and Related Materials (Withdrawn 1998)³
- D4214 Test Methods for Evaluating the Degree of Chalking of Exterior Paint Films
- D5870 Practice for Calculating Property Retention Index of Plastics
- E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

¹ This practice is under the jurisdiction of ASTM Committee D01 on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee D01.27 on Accelerated Testing.

Current edition approved June 1, 2011. Published August 2011. Originally approved in 1986. Last previous edition approved in 2005 as D4587 – 05. DOI: 10.1520/D4587-11.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For Annual Book of ASTM Standards volume information, refer to the standard's Document Summary page on the ASTM website.

³ The last approved version of this historical standard is referenced on www.astm.org.

TABLE 1 Test Cycles Commonly Used for Fluorescent UV-Condensation Exposure Testing of Paints and Related Coatings^A

Cycle Number	Cycle Description	340 nm Irradiance ^{B,C}	Black Panel Temperature ^D	Typical Uses ^E
1	8 h UV 4 h condensation Repeated continuously	0.83 W/(m ² ·nm) dark period	70 ± 2.5°C (158 ± 5°F) 50 ± 2. °C (122 ± 5°F)	Automotive coatings ^F
2	4 h UV 4 h condensation Repeated continuously	0.89 W/(m ² ·nm) dark period	60 ± 2.5 (140 ± 5°F) 50 ± 2.5 (122 ± 5°F)	Industrial maintenance coatings ^G
3	4 h UV 20 h condensation Repeated continuously	0.89 W/(m ² ·nm) dark period	60 ± 2.5 (140 ± 5°F) 50 ± 2.5 (122 ± 5°F)	Exterior wood coatings
4	8 h UV 4 h condensation Repeated continuously	0.89 W/(m ² ·nm) dark period	60 ± 2.5 (140 ± 5°F) 50 ± 2.5 (122 ± 5°F)	General metal coatings

^A The cycles described are not listed in any order indicating importance, and are not necessarily recommended for the applications listed. Additional exposure cycles are described in Practice G154.

^B The irradiance set point given is typical for devices operated without irradiance control. Other irradiance levels may be used, but must be described in the report.

^C Previous editions of Practice D4587 contained non-mandatory irradiance set points in Table 1 that were commonly used in the industry. The previous set points were 0.72 and 0.77 W/(m²·nm) at 340 nm for UVA 340 lamps. The measurement data used to establish these set points was inaccurate, due to an error in calibration on the part of one manufacturer. It has been found that, for most users, the actual irradiance when running at the previous set points was 11 to 15 % higher than the indicated set point. The set points shown in this edition of D4587 do not change the actual irradiances that have been historically used by these users. However, for users of equipment made by another manufacturer, the irradiance control system did not have the measurement inaccuracies described above, so running at the new set points will represent a change in the actual irradiance of the test. If in doubt, users should consult the manufacturer of their device for clarification.

^D Temperature is at equilibrium for either an uninsulated or insulated black panel, although the response of the insulated black panel might be slower than that for the uninsulated black panel. Refer to Practice G151 for more information about the construction and differences between uninsulated and insulated black panels.

^E Typical uses do not imply that results from exposures of these materials according to the cycle described will correlate to those from actual use conditions.

^F SAE J2020 describes the test used in many automotive specifications and requires use of a FS40 fluorescent UVB lamp.

^G Historical convention has established this as a very commonly used test cycle. This cycle may not adequately simulate the effects of outdoor exposure.

E1347 Test Method for Color and Color-Difference Measurement by Tristimulus Colorimetry

G53 Practice for Operating Light-and Water-Exposure Apparatus (Fluorescent UV-Condensation Type) for Exposure of Nonmetallic Materials (Withdrawn 2000)³

G113 Terminology Relating to Natural and Artificial Weathering Tests of Nonmetallic Materials

G141 Guide for Addressing Variability in Exposure Testing of Nonmetallic Materials

G147 Practice for Conditioning and Handling of Nonmetallic Materials for Natural and Artificial Weathering Tests

G151 Practice for Exposing Nonmetallic Materials in Accelerated Test Devices that Use Laboratory Light Sources

G154 Practice for Operating Fluorescent Ultraviolet (UV) Lamp Apparatus for Exposure of Nonmetallic Materials

G169 Guide for Application of Basic Statistical Methods to Weathering Tests

2.2 ISO Standard⁴

ISO 11507:1997 Paints and Varnishes—Exposure of Coatings to Artificial Weathering—Exposure to Fluorescent UV and Water

2.3 SAE Standard⁵

SAE J2020 Accelerated Exposure of Automotive Exterior Materials Using a Fluorescent UV Condensation Apparatus

3. Terminology

3.1 The definitions given in Terminology G113 are applicable to this practice.

⁴ Available from International Organization for Standardization (ISO), 1, ch. de la Voie-Creuse, Case postale 56, CH-1211, Geneva 20, Switzerland, <http://www.iso.ch>.

⁵ Available from SAE International (SAE), 400 Commonweath Dr., Warrendale, PA 15096-0001, <http://aerospace.sae.org>.

4. Significance and Use

4.1 The ability of a paint or coating to resist deterioration of its physical and optical properties caused by exposure to light, heat, and water can be very significant for many applications. This practice is intended to induce property changes associated with end-use conditions, including the effects of sunlight, moisture, and heat. The exposure used in this practice is not intended to simulate the deterioration caused by localized weather phenomena such as atmospheric pollution, biological attack, and saltwater exposure.

4.2 **Cautions**—Variation in results may be expected when different operating conditions are used. Therefore, no reference to the use of this practice shall be made unless accompanied by a report prepared according to Section 10 that describes the specific operating conditions used. Refer to Practice G151 for detailed information on the caveats applicable to use of results obtained according to this practice.

NOTE 3—Additional information on sources of variability and on strategies for addressing variability in the design, execution and data analysis of laboratory accelerated exposure tests is found in Guide G141.

4.2.1 The spectral power distribution of light from fluorescent UV lamps is significantly different from that produced in light and water exposure devices using other light sources. The type and rate of degradation and the performance rankings produced in exposures to fluorescent UV lamps can be much different from those produced by exposures to other types of laboratory light sources.

4.2.2 Interlaboratory comparisons are valid only when all laboratories use the same design of fluorescent UV device, lamp, and exposure conditions.

4.3 Reproducibility of test results between laboratories has been shown to be good when the stability of materials is evaluated in terms of performance ranking compared to other

materials or to a control.^{6,7} Therefore, exposure of a similar material of known performance (a control) at the same time as the test materials is strongly recommended. It is recommended that at least three replicates of each material be exposed to allow for statistical evaluation of results.

4.4 Test results will depend upon the care that is taken to operate the equipment according to Practice G154. Significant factors include regulation of line voltage, temperature of the room in which the device operates, temperature control, and condition and age of the lamps.

4.5 All references to exposures in accordance with this practice must include a complete description of the test cycle used.

5. Apparatus

5.1 Use of fluorescent UV apparatus that conform to the requirements defined in Practices G151 and G154 is required to conform to this practice.

NOTE 4—A fluorescent UV apparatus that complied with Practice G53 also complies with Practice G154.

5.2 Unless otherwise specified, the spectral power distribution of the fluorescent UV lamp shall conform to the requirements in Practice G154 for a UVA 340 lamp.

NOTE 5—Fluorescent UV exposures described in SAE J2020 for automotive applications call for use of fluorescent UVB lamps.

5.3 Test Chamber Location:

5.3.1 Locate the apparatus in an area maintained between 18 and 27°C (65 and 80°F). Measure ambient temperature at a maximum distance of 150 mm (6 in.) from the plane door of the apparatus. Control of ambient temperature is particularly critical when one apparatus is stacked above another, because the heat generated from the lower unit can interfere with the operation of the units above.

5.3.2 Place the apparatus at least 300 mm (12 in.) from walls or other apparatus. Do not place the apparatus near a heat source such as an oven.

5.3.3 Ventilate the room in which the apparatus is located to remove heat and moisture.

6. Hazards

6.1 **Warning**—In addition to other precautions, never look directly at the fluorescent UV lamp because UV radiation can damage the eye. Turn the device off before removing panels for inspection.

7. Test Specimens

7.1 Apply the coating to flat (plane) panels with the substrate, method of preparation, method of application, coating system, film thickness, and method of drying consistent with the anticipated end use, or as mutually agreed upon between the producer and user.

7.2 Panel specifications and methods of preparation include but are not limited to Practices D609, D1730, or Specification D358. Select panel sizes suitable for use with the exposure apparatus.

7.2.1 For specimens coated on insulating materials, such as foams, quickly check the specimens during the condensation period to verify that visible condensation is occurring on the specimens. Perform this visual check once per week at least one hour after the start of condensation.

NOTE 6—If condensation is not occurring, the most likely cause involves inadequate room-air cooling: (1) the laboratory temperature is too high; (2) condensation temperature is set too low, or too close to room temperature; (3) thick specimens of insulating material may be preventing the room-air cooling necessary for condensation. For example, a 25 mm thick wood specimen may exhibit poor condensation with a condensation set point of 40°C and a lab temperature of 30°C; or (4) improper specimen mounting is allowing vapor to escape from the chamber.

7.3 Coat test panels in accordance with Practices D823, then measure the film thickness in accordance with an appropriate procedure selected from Test Methods D1005, D1186, or D1400. Nondestructive methods are preferred because panels so measured need not be repaired.

7.4 Prior to exposing coated panels in the apparatus, condition them at 23 ± 2°C (73 ± 3°F) and 50 ± 5 % relative humidity for one of the following periods in accordance with the type of coating:

Baked coatings	24 h
Radiation-cured coatings	24 h
All other coatings	7 days

7.4.1 Other procedures for preparation of test specimens may be used if agreed upon by all interested parties.

7.5 Mount specimens in holders so that only the minimum specimen area required for support by the holder is covered. Do not use this covered area of the specimen as part of the test area.

7.6 Unless otherwise specified, expose at least three replicate specimens of each test and control material.

7.7 Follow the procedures described in Practice G147 for identification and conditioning and handling of specimens of test, control, and reference materials prior to, during, and after exposure.

7.8 Do not mask the face of a specimen for the purpose of showing on one panel the effects of various exposure times. Misleading results may be obtained by this method, since the masked portion of the specimen is still exposed to temperature and humidity cycles that in many cases will affect results.

7.9 Retain a supply of unexposed file specimens of all materials evaluated.

7.9.1 When destructive tests are run, it is recommended that a sufficient number of file specimens be retained so that the property of interest can be determined on unexposed file specimens each time exposed materials are evaluated.

NOTE 7—Since the stability of the file specimen may also be time dependent, users are cautioned that over prolonged exposure periods, or where small differences in the order of acceptable limits are anticipated, comparison of exposed specimens with the file specimen may not be valid.

⁶ Fischer, R., "Results of Round Robin Studies of Light- and Water-Exposure Standard Practices," *Accelerated and Outdoor Durability Testing of Organic Materials*, ASTM STP 1202, ASTM, 1993.

⁷ Ketola, W., and Fischer, R., "Characterization and Use of Reference Materials in Accelerated Durability Tests," *VAMAS Technical Report No. 30*, NIST, June 1997.

Nondestructive instrumental measurements are recommended whenever possible.

7.10 Specimens should not ordinarily be removed from the exposure apparatus for more than 24 h, then returned for additional tests, since this may not produce the same results on all materials as tests run without this type of interruption. When specimens are removed from the exposure apparatus for 24 h or more, then returned for additional exposure, report the elapsed time as noted under Section 10.

8. Procedure

8.1 Table 1 lists several exposure cycles that are used for fluorescent UV exposures of nonmetallic materials. Obtain agreement between all concerned parties for the specific exposure cycle used. Additional intervals and periods of condensation may be substituted upon agreement among the concerned parties.

NOTE 8—Each setpoint and its tolerances found in Table 1 represent an operational control point for equilibrium conditions at a single location in the cabinet, which may not necessarily represent the uniformity of those conditions throughout the cabinet. ASTM Committee G03 is working to refine these tolerances and address the uniformity issue.

8.2 If no other cycle is specified, use Cycle 2.

8.3 Mount test specimens in the device following the placement and specimen repositioning procedures described in Practice G154.

8.3.1 Fill any empty spaces in the exposure area with blank nonrusting panels. Seal any holes in specimens larger than 2 mm (0.08 in.) and any openings larger than 1 mm (0.04 in.) around irregularly shaped specimens to prevent loss of water vapor. Attach porous specimens to a solid backing such as aluminum that can act as a vapor barrier.

8.3.2 Reposition specimens in devices with a planar exposure area using the following procedure unless it can be shown that the irradiance uniformity meets the requirements of Practice G151 for no repositioning. In devices that do not have a planar exposure area, reposition specimens using a procedure agreed upon by all interested parties.

8.3.2.1 *Repositioning Procedure*—Unless otherwise specified, move the two extreme right-hand holders to the far left of the exposure area, and slide the remaining holders to the right. Fig. 1 shows the repositioning of specimen holders.

8.3.2.2 Unless otherwise specified, reposition specimens vertically within each specimen holder so that each spends the same amount of exposure time in each vertical position within the specimen holder. Fig. 2 shows the vertical rotation sequence for cases where there are two, three, or four specimens in a holder.

NOTE 9—In devices without irradiance control, incident energy at the extremes of the exposure area is often only 70 % of that at the center. This condition requires that the procedures described in 8.3 be followed to ensure uniformity of radiant exposure.

8.3.3 *Repositioning Frequency*—Unless otherwise specified, the repositioning frequency shall be 10 % of the exposure increment between evaluations.

8.4 *Water Purity*:

8.4.1 It is recommended that deionized water be used for water used to produce condensation.

8.5 Identification of any control specimen used shall accompany the report.

9. Periods of Exposure and Evaluation of Results

9.1 In most cases, periodic evaluation of test and control materials is necessary to determine the variation in magnitude and direction of property change as a function of exposure time or radiant exposure.

9.2 The time or radiant exposure necessary to produce a defined change in a material property can be used to evaluate or rank the stability of materials. This method is preferred over evaluating materials after an arbitrary exposure time or radiant exposure.

9.2.1 Exposure to an arbitrary time or radiant exposure may be used for the purpose of a specific test if agreed upon by the parties concerned or if required for conformance to a particular specification. When a single exposure period is used, select a time or radiant exposure that will produce the largest performance differences between the test materials or between the test material and the control material.

9.2.2 The minimum exposure time used shall be that necessary to produce a substantial change in the property of interest for the least stable material being evaluated. An exposure time that produces a significant change in one type of material cannot be assumed to be applicable to other types of materials.


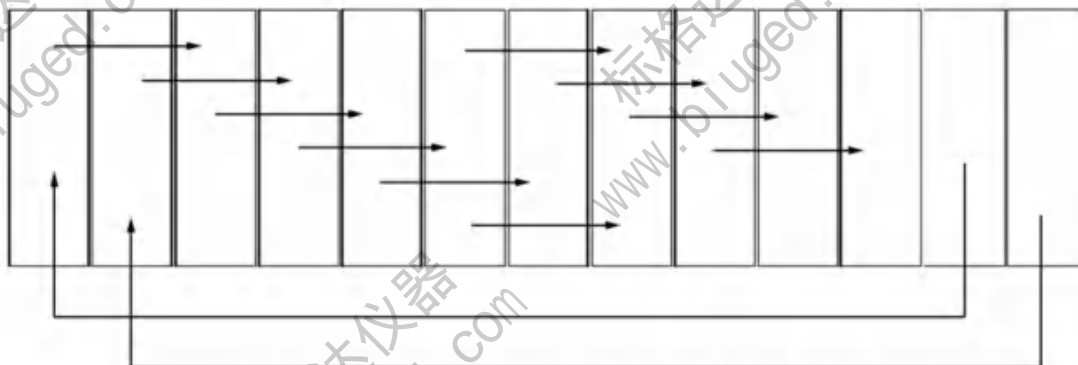


FIG. 1 Diagram Showing Repositioning of Specimen Holders

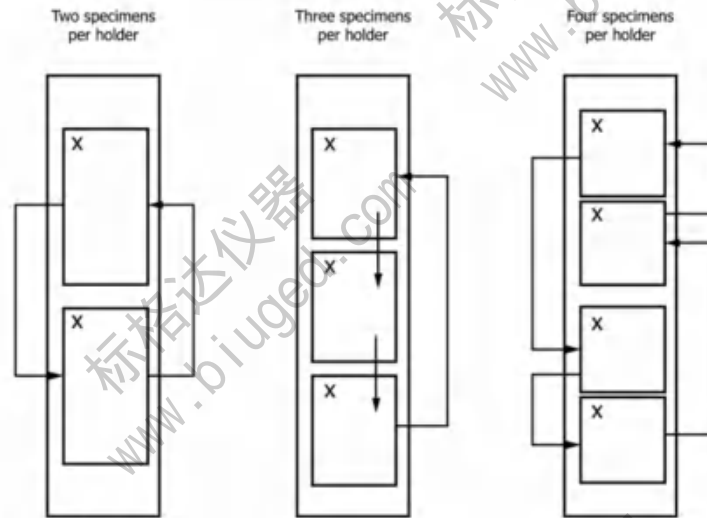

NOTE 1—"X" denotes orientation of each specimen.

FIG. 2 Specimen Repositioning Within Holders

9.2.3 The relation between time to failure in an exposure conducted according to this practice and service life in an outdoor environment requires determination of a valid acceleration factor. Do not use arbitrary acceleration factors relating time in an exposure conducted according to this practice and time in an outdoor environment because they can give erroneous information. The acceleration factor is material dependent and is only valid if it is based on data from a sufficient number of separate exterior and laboratory accelerated exposures so that results used to relate times to failure in each exposure can be analyzed using statistical methods.

NOTE 10—An example of a statistical analysis using multiple laboratory and exterior exposures to calculate an acceleration factor is described by J.A. Simms.⁸ See Practice G151 for more information and additional cautions about the use of acceleration factors.

9.3 After each exposure increment, determine the changes in exposed specimens. Test Method D523, D610, D659, D660, D662, D714, D772, D2244, D2616, D3359, D4214, E1347 or Practice D1729 may be used. Consider product use requirements when selecting appropriate methods.

9.3.1 Other methods for evaluating test specimens may be used if agreed upon between all interested parties.

NOTE 11—For some materials, changes may continue after the specimen has been removed from the exposure apparatus. Measurements (visual or instrumental) should be made within a standardized time period or as agreed upon between interested parties. The standardized time period needs to consider conditioning prior to testing.

9.4 It is recommended that the following procedure be followed when results from exposures conducted according to this practice are used in specifications.

9.4.1 If a standard or specification for *general use* requires a defined property level after a specific time or radiant exposure in an exposure test conducted according to this practice, base the specified property level on results from round-robin experiments run to determine the test reproduc-

ibility from the exposure and property measurement procedures. Conduct these round robins according to Practice E691 or D3980 and include a statistically representative sample of all laboratories or organizations that would normally conduct the exposure and property measurement.

9.4.2 If a standard or specification for *use between two or three parties* requires a defined property level after a specific time or radiant exposure in an exposure test conducted according to this practice, base the specified property level on at least two independent experiments run in each laboratory to determine the reproducibility for the exposure and property measurement process. The reproducibility of the exposure/property measurement process is then used to determine the maximum or minimum level of property after the exposure that is mutually agreeable to all parties.

9.4.3 When reproducibility in results from an exposure test conducted according to this practice has not been established through round-robin testing, specify performance requirements for materials in terms of comparison (ranked) to a control material. All specimens shall be exposed simultaneously in the same device. All concerned parties must agree on the specific control material used.

9.4.3.1 Conduct analysis of variance to determine whether the differences between test materials and any control materials used are statistically significant. Expose replicates of the test specimen and the control specimen so that statistically significant performance differences can be determined.

NOTE 12—Fischer illustrates use of rank comparison between test and control materials in specifications.⁹

NOTE 13—Guide G169 includes examples showing use of analysis of variance to compare materials.

⁸ Simms, J.A., *Journal of Coatings Technology*, Vol. 50, 1987, pp. 45-53.

⁹ Fischer, R., Ketola, W., "Impact of Research on Development of ASTM Durability Testing Standards," *Durability Testing of Non-Metallic Materials*, ASTM STP 1294, ASTM, 1995.

10. Report

10.1 Report the following information:

10.1.1 Type and model of exposure device.

10.1.2 Type of light source.

10.1.3 Average distance from specimens to light source.

10.1.4 Age of lamps at the beginning of the exposure, and whether any of the lamps were replaced during the period of exposure.

10.1.5 Type of black panel (uninsulated or insulated) used.

10.1.6 If required, report irradiance measured at a single wavelength in $W/(m^2 \cdot nm)$ and radiant energy for a single wavelength in $J/(m^2 \cdot nm)$. Report irradiance measured in a broad band, such as 300-400 nm, in W/m^2 with the spectral region specified. Report radiant energy measured in a broad band as J/m^2 with the spectral region specified.

10.1.6.1 Do not report irradiance or radiant exposure unless direct measurement of irradiance was made during the exposure.

10.1.7 Elapsed exposure time.

10.1.7.1 When required, report any test interruptions greater than 24 h in accordance with 7.10.

10.1.8 Light and dark-water-condensation cycle employed.

10.1.9 Operating black panel temperature.

10.1.10 Operating relative humidity during light exposure (if measured).

10.1.11 Specimen repositioning procedure (if different from that described in 8.4).

10.1.12 Results of property tests. Where retention of characteristic property is reported, calculate results according to Practice D5870.

NOTE 14—In some cases, exposures are conducted by a contracting agency but property tests are conducted by the contracting party. In these cases, the agency that conducts the exposures cannot report results from property tests.

11. Precision and Bias

11.1 *Precision*—The repeatability and reproducibility of results obtained in exposures conducted according to this practice will vary with the materials being tested, the material property being measured, and the specific test conditions and cycles that are used.

11.2 *Bias*—Bias can not be determined because no acceptable standard weathering reference materials are available.

12. Keywords

12.1 degradation; exposure; fluorescent UV; light exposure; ultraviolet; weathering

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/